


Sto High-Strength Shotcrete

CR305

Division 3

patching and repair mortar
vertical/overhead
microsilica-fortified
dust-controlled

**cement-based, using
proprietary StoCrete
technology**

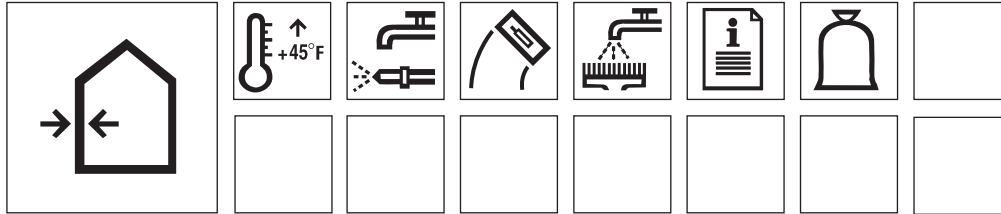

Technical Data

REPORT	TEST METHOD	CRITERIA	TEST RESULTS
Working Time (minutes)			10-20
Compressive Strength (psi)	ASTM C-109	1 day 3 day 7 days 28 days	4,000 6,000 7,500 8,500
Bond Strength (psi)	ASTM C-882 Modified	7 days 28 days	2,000 2,500
Flexural Strength (psi)	ASTM C-78	7 days 28 days	1,000 1,750
Modulus of Elasticity in Compression (psi)	ASTM C-469	28 days	< 3.8 x 10 ⁶
Splitting Tensile Strength (psi)	ASTM C-496	7 days 28 days	800 1,200
Shrinkage (%)	ASTM C-157	7 days 28 days	< 0.06 < 0.08
Rapid Chloride Permeability (Coulombs)	AASHTO T-277 ASTM C-1202	28 days	< 250

*Typical values for material cured at 73° F (23° C) and 50% R.H.

Note: To convert psi to megapascal (Mpa) multiply by 0.0069.

Sto High-Strength Shotcrete is a durable, cement-based, dry-process shotcrete mortar for structurally repairing deteriorated concrete. It has been fortified with microsilica for superior physical strengths. Use it on vertical or overhead surfaces for repairs greater than 1/2 inch (12 mm).

Volume Yield

0.40 ft³ per 55-lb bag (0.014 m³ per 25-kg bag)

Packaging

55-lb bag (25 kg)

Shelf Life

12 months in original unopened container.

Storage

Store in a dry area between 50° F (10° C) and 85° F (29° C). Protect from direct sunlight.

Features

Benefits

- | | |
|----------------------------------------------------|---------------------------------------------------------------------------------|
| 1 Microsilica-fortified | High bond and higher compressive strengths; reduces permeability and shrinkage |
| 2 Non-sag, low slump | Hangs easily without sagging; increases job-site productivity |
| 3 Extremely low shrinkage | Stable bond line; resists perimeter cracking |
| 4 Thermally compatible with concrete | Prevents delamination caused by temperature changes |
| 5 Very low chloride permeability | Protects embedded steel against corrosion |
| 6 Low rebound and dust | More stays on the substrate, increasing yield per bag; usable in confined areas |

Surface Preparation

Remove loose and deteriorated concrete by mechanical chipping or sand-blasting to obtain a fractured aggregate surface. Detail the edge of the patch to a 90° angle to eliminate feather edging. Make sure surfaces are sound, clean, and free of all bond-inhibiting materials including oil, dirt, dust, laitance and standing water.

Mixing

Use Sto High-Strength Shotcrete at a pre-conditioned temperature of 70 ± 5° F (21 ± 3° C).

Mix Sto High-Strength Shotcrete using standard dry-process equipment. This equipment mixes and sprays the product using the following components.

Gun: pressurizes product.

Material hose: conveys product to the nozzle.

Water hose: conveys water to the nozzle.

Water ring: injects water into product as it enters the nozzle.

Nozzle: discharges mixed material onto the substrate.

Once the product is sprayed on the substrate, the working time is 10-20 minutes, depending upon material, ambient and surface conditions.

Application

Dampen the area to be repaired so that the pores of the concrete are filled with water. Remove any ponding or glistening water on the surface (saturated surface dry/SSD).

IMPORTANT: The quality of a shotcrete application depends to a large extent on the experience of the nozzleman.

Apply Sto High-Strength Shotcrete following the American Concrete Institute's "Guide to Shotcrete" (ACI 506R-85).

Holding the nozzle at a 90° angle from the substrate and moving it in a circular motion will ensure proper consolidation of the product and reduce rebound.

Once applied, Sto High-Strength Shotcrete can be left rough or cut with a trowel and finished with a sponge float for a slightly textured finish.

Applications made during temperatures below 50° F (10° C) or above 85° F (29° C) should follow the appropriate application guidelines.

Curing

Direct sun or wind may cause unwanted rapid surface drying. Curing may be accomplished by continuous water fogging for 48 hours or cover with damp burlap or burlene curing blankets. Do not use solvent-based curing compounds or allow water to puddle. If a coating or sealer will be applied, use water fogging or blanket curing methods and prep finished surface per manufacturer's recommendations.

Clean Up

Clean tools and equipment with water immediately after use. Cured material can only be removed mechanically.

How It's Used

Sto High-Strength Shotcrete is a vertical and overhead shotcrete repair mortar that is ready to use. Once mixed with clean water by standard dry-process shotcrete equipment, it hangs overhead without falling. Its low rebound reduces waste, increasing yield per bag and job-site productivity. Use it for repairs greater than ½ inch (12 mm).

Health And Safety

Health Precautions

Contains Portland cement and crystalline-free silica. Avoid breathing dust. As with any chemical construction product, exercise care when handling.

Safety Precautions

Use adequate ventilation. Use of a NIOSH/MSA-approved dust respirator, safety goggles and protective gloves are recommended.

First Aid

SKIN CONTACT: Wash hands thoroughly with soap and water

EYE CONTACT: Flush immediately with water for 10-15 minutes and contact a physician.

RESPIRATORY PROBLEMS: Remove affected person to fresh air immediately and contact a physician.

HYGIENE: Wash hands immediately after use. Wash clothing before reuse.

Spills

Collect in an appropriate container. Uncured material may be removed with water.

Disposal

Dispose of in accordance with local, state or federal regulations.

Warning

KEEP CONTAINER CLOSED WHEN NOT IN USE. KEEP OUT OF THE REACH OF CHILDREN. NOT FOR INTERNAL CONSUMPTION. FOR INDUSTRIAL USE ONLY. Consult the Material Safety Data Sheet for further health and safety information.

LIMITED WARRANTY

THIS PRODUCT IS SUBJECT TO A WRITTEN LIMITED WARRANTY WHICH CAN BE OBTAINED FREE OF CHARGE FROM: Sto Corp., 3800 Camp Creek Parkway, Building 1400, Suite 120, Atlanta, GA 30331; Tel: 404-346-3666; Fax: 404-346-3119

Sto Corp.

3800 Camp Creek Parkway
Building 1400, Suite 120
Atlanta, GA 30331
Tel: 404-346-3666
Toll Free: 1-800-221-2397
Fax: 404-346-3119
www.stocorp.com



Limitations

- Apply only when the surface and ambient temperature are 45-50° F (7-10° C) and rising. See Cold Weather Application guidelines, per ACI for applications in temperatures less than 50° F (10° C). Applications made during temperatures greater than 85° F (29° C) should follow Hot Weather Application guidelines, per ACI.
- The minimum required thickness is ½ inch (12 mm). To obtain a copy of ACI 506R-85 "Guide to Shotcrete" contact Technical Services.